

Thermal Conductivity of Covalent-Organic Frameworks

Jinha Kwon, Hao Ma, Ashutosh Giri, Patrick E. Hopkins, Natalia B. Shustova, and Zhiting Tian*



Cite This: *ACS Nano* 2023, 17, 15222–15230



Read Online


ACCESS |

Metrics & More

Article Recommendations

ABSTRACT: Covalent-organic frameworks (COFs) are a highly promising class of materials that can provide an excellent platform for thermal management applications. In this Perspective, we first review previous works on the thermal conductivities of COFs. Then we share our insights on achieving high, low, and switchable thermal conductivities of future COFs. To obtain the desired thermal conductivity, a comprehensive understanding of their thermal transport mechanisms is necessary but lacking. We discuss current limitations in atomistic simulations, synthesis, and thermal conductivity measurements of COFs and share potential pathways to overcoming these challenges. We hope to stimulate collective, interdisciplinary efforts to study the thermal conductivity of COFs and enable their wide range of thermal applications.

KEYWORDS: covalent-organic frameworks, thermal conductivity, thermal management

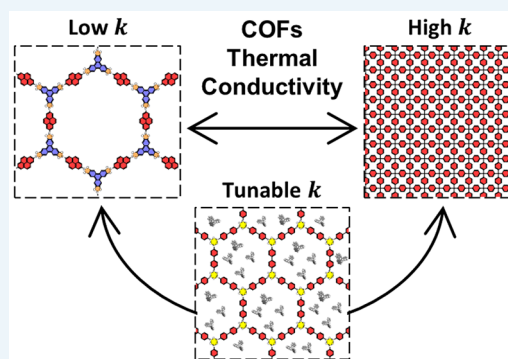

INTRODUCTION

COFs are an emerging class of crystalline porous materials usually consisting of light elements (B, C, N, O, Si) linked via strong covalent bonds. Particularly, COFs are fully pre-designable polymers with designated pore apertures, ordered channel structures, and versatile chemical compositions.¹ Their cage-like structures with large surface areas result in COFs being considered candidates for gas capture, storage, and separation systems. Moreover, their modular and periodic architectures make them attractive for diverse fields of catalysis, chemosensing, optoelectronics, and drug delivery.²

The COF synthesis is primarily based on fundamental concepts of dynamic covalent chemistry.³ Preparation of COFs or COF-containing materials typically relies on the use of Schiff base reactions, self-condensation of boronic acid, or reactions between boronic acid and catechol-based linkers. Recently, a synthetic approach utilizing multisubstituted monomers was successfully applied to prepare two-dimensional COFs. The last method allowed for the integration of organic linkers containing heavy elements, enhancing the COF structural diversity. Another powerful and commonly employed synthetic methodology is a COF's postsynthetic modification with desired multifunctional moieties, allowing frameworks' properties to be tailored after the material synthesis.⁴ A COF is highly dependent on the formation of dynamic bonds, which allows for self-correction to occur. However, the presence of highly robust bonds in COF structures is driven by industrial demands, and therefore, the

COF synthesis is a compromise between crystallinity and structural framework integrity. The current trends in the COF field integrate studies of COF morphology and its effect on material properties,⁵ reconstruction routes for enhancement of framework crystallinity and porosity, and on-surface COF synthesis.^{6,7}

Although a considerable amount of research has been carried out to understand a range of physical and chemical properties of COFs, their thermal transport mechanisms have received far less attention. However, COFs can be engineered to possess exceptional thermal functionalities for various applications, as illustrated in Figure 1. One advantage of COFs is the extensive control over pore sizes and shapes facilitated by diverse combinations of organic building units based on carbon chemistry. Moreover, compared to metal-organic frameworks (MOFs), COFs are generally more thermally and chemically stable due to the stronger covalent bonds holding the framework together and absence of metals prone to reduction, making COFs potentially more suitable for use in harsh environments or high temperatures than MOFs.⁸

Received: April 19, 2023

Accepted: August 2, 2023

Published: August 8, 2023



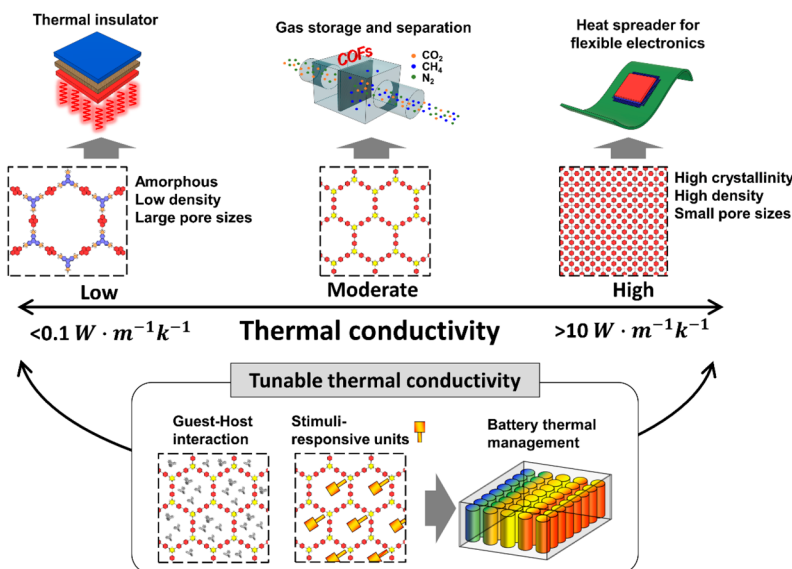


Figure 1. Schematic of the various thermal conductivities of COFs. COFs with low thermal conductivity have low density and large pore sizes, which can be used as thermal insulators. In contrast, COFs with high thermal conductivity possess high crystallinity, high density, and small pore sizes with potential applications as lightweight heat spreaders for electronics, including flexible electronics. The thermal conductivity of COFs can be tuned by guest–host interactions or integration with stimuli-responsive units, which can be potentially used for on-demand thermal management applications, such as battery thermal management modules.

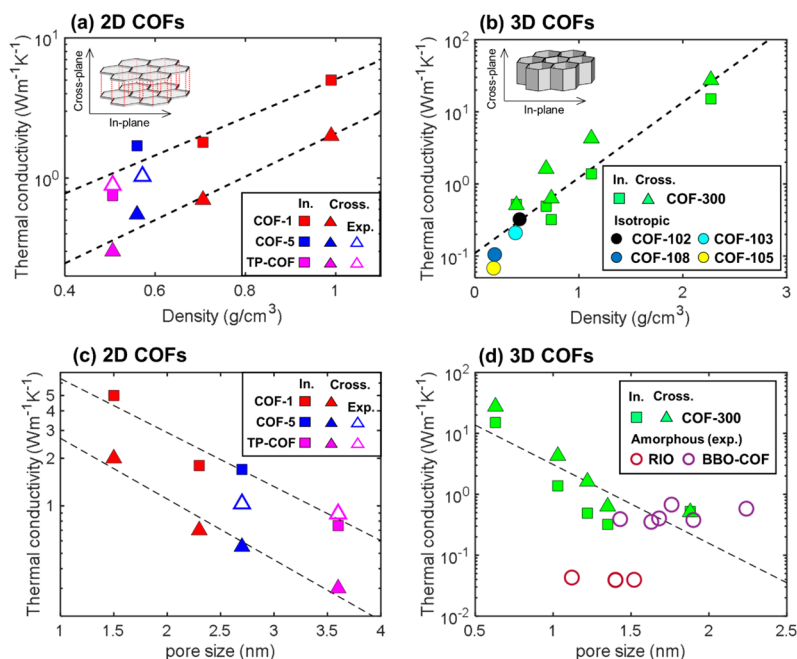


Figure 2. Thermal conductivities of (a) 2D and (b) 3D COFs as a function of their densities. The rectangular, triangular, and circular shapes indicate the in-plane, cross-plane, and isotropic thermal conductivities, respectively. COF-1 (red), COF-5 (blue), and TP-COF (magenta) are plotted in 2D COFs, while COF-300 and its derivatives (green), COF-102 (black), COF-103 (cyan), COF-108 (dark blue), and COF-105 (yellow) are plotted in 3D COFs. Thermal conductivities of (c) 2D COFs and (d) 3D COFs as a function of their pore sizes. All thermal conductivities were from MD simulations except the unfilled triangles for COF-5 (blue) and TP-COF (magenta) in (a) and (c) and unfilled circles for RIO powder (brown) and BBO-COF pellets (purple) in (d), which are experimental thermal conductivities.

The large tunability in the nanostructured architecture of COFs based on hierarchical manipulation of the chemical structure and morphology provides the opportunity not only to obtain low thermal conductivities like other porous materials but also to attain high thermal conductivities that other porous materials have difficulty in attaining, providing solutions for various thermal applications. For instance, a 2D COF layer

engineered to obtain high thermal conductivity with ultralow dielectric permittivity can be utilized for nanoscale integrated circuit components, reducing the parasitic capacitance effect.⁹ Furthermore, attaining high thermal conductivities with strong bonds in COF positions them as ideal candidates for lightweight thermal management applications in flexible electronics and traditional microelectronics.^{1,10} In addition,

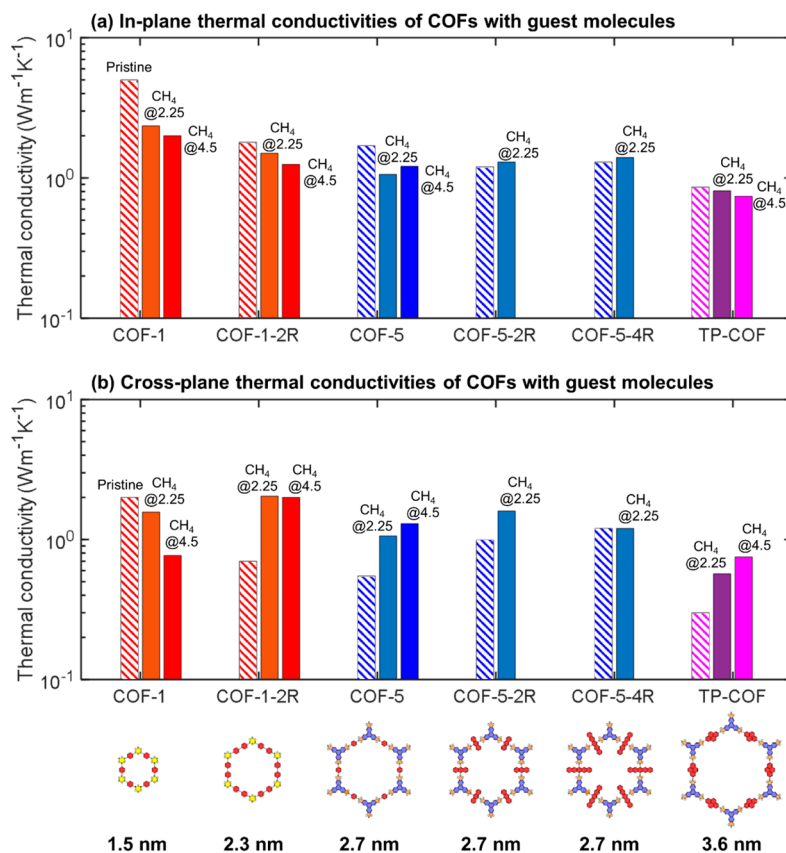


Figure 3. Comparison of (a) in-plane and (b) cross-plane thermal conductivities between pristine and infiltrated COFs filled with gas molecules (CH_4 (methane)) via MD simulations. The hatched bars indicate pristine COFs, while the filled bars denote infiltrated COFs. The concentration of CH_4 is shown with units of the gas density (molecules/ nm^3).

2D COFs inherently show anisotropic thermal conductivity, which can be employed for heat-spreading applications, where higher thermal conductivities are preferred in certain directions. Beyond these applications, recent computational studies have shown that the thermal conductivity of COFs can be tuned by guest–host interactions, such as by filling the nanopores with guest molecules,^{11,12} suggesting potential thermal switch applications. Although COFs have shown plenty of opportunities for diverse thermal applications, the underlying thermal transport mechanisms of COFs have not been comprehensively understood.

This perspective first reviews previous studies of the thermal conductivities of various COFs and then suggests potential ways to achieve high, low, and tunable thermal conductivity. Additionally, it presents the current challenges and possible solutions in COF synthesis, atomistic simulations, and thermal conductivity measurements to gain a deeper understanding of COFs' thermal transport properties.

REVIEW OF PREVIOUS WORK

Thermal Conductivity of Pristine COFs. A broad spectrum of thermal conductivity values has been reported for COFs. For amorphous COFs, the experimental study on powdered 3D COFs, such as reticular innovative organic materials (RIOs) and COF-300, exhibited even lower thermal conductivities of less than $0.05 \text{ W m}^{-1} \text{ K}^{-1}$ at room temperature.¹³ On the other hand, crystalline COFs have displayed high thermal conductivities. For instance, boronate

ester-linked 2D COF films, namely TP-COF and COF-5, were experimentally measured to possess thermal conductivities of 0.89 and $1.03 \text{ W m}^{-1} \text{ K}^{-1}$ in the direction of the laminar pores (cross-plane direction), respectively, which were attributed to their structural regularity, crystallinity, and relatively strong interlayer interactions.⁹ MD simulations showed that a 3D COF-300 derivative with extremely narrow pores (0.63 nm) exhibits an exceptionally high thermal conductivity of $>15 \text{ W m}^{-1} \text{ K}^{-1}$ in all directions.¹⁴

Figure 2 summarizes the reported thermal conductivities of pristine 2D and 3D COFs. Figure 2a,b shows the thermal conductivities of 2D and 3D COFs with respect to their densities containing pores. Typically, the in-plane direction is defined as perpendicular to the pore axes, whereas the cross-plane direction is defined as parallel to the pore axes, as depicted in the insets of Figure 2a,b. In both 2D and 3D COFs, a clear ascending trend of thermal conductivities with respect to their densities is observed, as expected. Inherently, 2D COFs display large anisotropic thermal conductivities owing to the distinct interactions that strong covalent bonds occur within the 2D layers while relatively weak van der Waals interactions exist between the layers.⁹ For 3D COFs, COF powders (solid filled circles in Figure 2b) show low experimental thermal conductivities due to their amorphous morphology.¹⁵ On the other hand, MD simulations show that crystalline 3D COF-300 derivatives (green markers) exhibit high thermal conductivities.¹⁴ 3D COFs exhibit relatively low anisotropic thermal conductivity compared to 2D COFs because of continuous heat conduction pathways formed by

strong covalent bonds in all directions.¹⁴ Figure 2c,d displays the pore size dependence of the thermal conductivities in 2D and 3D COFs. The thermal conductivities of 2D and 3D COFs decrease as the pore size increases, resulting from the proportionality between the number of lattice vibrational modes (phonons) and the number of chain crossings per unit area. However, RIO and BBO-COF in Figure 2d are not following this trend^{13,16} probably because RIOs are prepared in powder form, and BBO-COFs are made as pellets by compressing COF powder. This amorphous form of COFs strongly scatters the heat carriers and thus is less sensitive to the pore size. Note that a direct comparison of the experimental results with MD simulations warrants caution at this stage, given the different conditions, such as sample morphology, crystallinity, or defects and the lack of accurate interatomic potentials. For instance, the experimental values of COF-5 (blue) and TP-COF (magenta), indicated by unfilled triangles in Figure 2a,c, demonstrate higher cross-plane thermal conductivities compared to the MD results. This discrepancy could be attributed to the insufficiencies of the interatomic potentials used in the MD simulation.⁹ A detailed discussion of the current challenges encountered in MD simulations is presented later.

Thermal Conductivity of Infiltrated COFs. Introducing guest molecules into COFs can modify their thermal conductivities, and the effects on thermal conductivity are case-dependent. Figure 3 compares the thermal conductivities of pristine and guest-infiltrated 2D COFs via MD simulations. Notably, the dependence of the thermal conductivities on the infiltration of guests is nonmonotonic. There are competing effects of enhancing scattering, increasing density, and adding extra heat conduction paths, and which of these effects dominates depends on the pore sizes. For COFs with small pores, such as COF-1, the addition of guest molecules mainly enhances solid–gas scattering and results in decreased thermal conductivities in both in-plane and cross-plane directions.¹⁷ For COFs with large pores, such as COF-1-2R, COF-5, and TP-COF, the additional heat conduction channels enabled by guest molecules play a more dominant role and lead to increased cross-plane thermal conductivities, while the resulting scattering effects reduce or maintain similar in-plane thermal conductivities compared to the unfilled COFs.¹² Note that the small in-plane thermal conductivity differences between 2.25 and 4.5 molecules/nm³ for COF-5 and TP-COF are within the simulation errors.^{12,17} Interestingly, additional phenyl rings of COF-5, as shown in Figure 3, introduce additional in-plane scattering while disturbing the gas flow in the cross-plane direction.¹²

PERSPECTIVE FOR FUTURE DIRECTIONS

High Thermal Conductivity. In order to achieve high thermal conductivity, several important factors need to be considered, including dense structure with tiny pores, high crystallinity, and certain guest interactions.^{9,14,17} A straightforward way to increase the thermal conductivity of COFs is to build a dense network with small pores or a highly interpenetrated structure with high crystallinity.¹⁸ A denser network not only increases the density but also limits the rotational degree of freedom of the linkers and normally results in higher crystallinity.

The crystal network topologies of the COFs can play a role. In the case of MOFs, it was reported that the topologies possessing 4-connected nodes exhibited surprisingly high

thermal conductivity. This behavior may be attributed to the favorable alignment of strong covalent bonds along the direction of heat transfer.¹⁹ Interestingly, the COF-300 derivative that exhibited ultrahigh thermal conductivity also has a 4-connected topology. Thus, leveraging a desired primitive topology of COFs can potentially enhance COFs' thermal conductivity.

Stronger bonds are generally preferred for better heat conduction.²⁰

Conjugation. COFs exhibit a high degree of conjugation, which can be beneficial to achieve high thermal conductivity.^{21–23} For example, π -conjugated crystalline linear²⁰ and 2D polymers^{22,24} with large bond energy in their backbones show large thermal conductivity. In this regard, the extended conjugation in COFs can promote the propagation of phonons along the framework, leading to increased thermal conductivity.

Robust Linker. Recently, COFs with robust bonds developed by multicomponent reactions or strengthening covalent linkages to overcome their inherent chemical stability issues have been developed.^{25,26} The introduction of stronger covalent linkages in robust COFs can enhance thermal conductivity if everything else is kept the same. However, it is essential to consider that the enhanced stability of robust COFs may come at the cost of reduced reversibility in linkage formation, which can affect error correction and defect-healing processes that are crucial for maintaining high crystallinity in COFs.

If isotropically high thermal conductivity is desired, 3D COFs can be a good candidate because they inherently give more isotropic heat conduction than 2D COFs. If 2D COFs are preferred, given the easier synthesis conditions, there are also ways to improve its cross-plane thermal conductivity.

Backbone Modification. For example, COF-5-2R and COF-5-4R show larger cross-plane thermal conductivities by introducing additional phenyl rings into COF-5, as shown in Figure 3. These additional phenyl rings can increase the solid surface area and introduce extra π – π stacking interactions between the layers, enhancing cross-plane thermal conductivity. Meanwhile, these phenyl rings have a small impact on in-plane heat conduction.

Guest Filler Infiltration. Guest molecules like methane infiltrate and diffuse along the pore channels allow additional cross-plane heat conduction. For instance, instead of using methane gas, filling the pore with crystalline polymers with high thermal conductivity may provide more efficient heat transfer pathways.²⁷ However, the relative difference between pore size and filler size, the filler density, the guest–host interaction strength, the intactness of the framework are all important factors to consider.

2D COF Interpenetration.^{28,29} Essentially, one can build a 3D network from 2D COFs. The constructed 3D network exhibited a dramatic increase in thermal conductivity while maintaining the same mass density as traditional 3D frameworks.²⁹ This superior thermal conductivity was attributed to the enhanced phonon hardening and shift of heat-carrying vibrations to higher frequencies, resulting from the supramolecular interactions between the 2D frameworks.

Low Thermal Conductivity. Opposite approaches from above can be taken to achieve low thermal conductivity: for example, developing amorphous COFs in powder form with large pores and lower density. Besides, the wall grafting technique could be adapted to induce a gas–solid scattering

effect. As shown in the COF-5 case,¹² small amounts of gas infiltration into COF-5 (i.e., methane gas with 2.24 molecules/nm³) is likely to increase the gas–solid scattering rather than create additional heat transfer paths, resulting in the reduction of in-plane thermal conductivity.

Moreover, exploiting specific polymer guests could decrease the thermal conductivity. For instance, the BBO-COFs doped with poly(3-hexylthiophene) (p3HT) were reported to give lower thermal conductivity compared to undoped BBO-COFs, because the filling of p3HT polymers disrupted some of the π – π stacking between the BBO-COF layer.¹⁶ Therefore, introducing guest molecules that are large enough to disrupt or distort the covalent network in the COFs is another strategy to create COFs with low thermal conductivity.

Tunable Thermal Conductivity. To achieve tunable thermal conductivity, a contrast between the initial and final states through structural or interaction changes is needed. The gas–solid interaction in COFs offers one way to develop tunable thermal conductivity. Based on the MD simulations, the infiltrated methane gas can either decrease or increase the thermal conductivity. The infiltration ratio of guest materials could be controlled to regulate the thermal conductivity. Further investigations into the complexities of guest–host interactions are still needed to understand the effect of different types of guest–host chemistries on thermal transport. Moreover, the inclusion of solvent molecules as guests could be considered. Solvent molecules typically have larger sizes and greater molecular weights compared with gas molecules, which can lead to distinct effects on phonon propagation within COFs. The presence of solvent molecules can induce structural changes, converting the COF framework from a robust system to a more dynamic one, as observed in MOF-5.^{30,31} Additionally, solvent–COF interactions may influence vibrational lifetimes and alter the character of vibrational modes, promoting the emergence of localized incoherent modes over a broad range of frequencies, as exemplified by the HKUST-1 system.³² Considering these factors, the thermal conductivity of COFs in the presence of solvent molecules may significantly deviate from that in the dry state. Further investigation is needed to gain insight into the solvent effect on the thermal conductivity of COFs and to optimize their performance in specific environments.

The second strategy to achieve tunable thermal conductivity is to integrate stimuli-responsive units into a rigid COF matrix as a part of the COF backbone, whose phase transition could disrupt the structural order and thereby alter thermal transport in response to external stimuli.⁴ Similar to the case of photoswitchable MOFs,³³ the framework built by stimuli-responsive units, such as photoisomerization of azobenzene,³⁴ or magnetic stimuli with mesogen,³⁵ could achieve controllable morphology and thus tunable thermal conductivity. One can also introduce stimuli-responsive units to graft or modify the COF walls. For instance, adsorbed species and functional attachments of stimuli-responsive units on the pore walls of COFs could alter the free space volume of the pores through contraction or expansion of the functional moieties, changing the porosity of the COFs and, thus, the thermal transport properties. We envision that the thermal conductivity of COFs can be switched on demand using different stimuli, including electrical, magnetic, thermal, and optical.

CURRENT CHALLENGES AND POTENTIAL SOLUTIONS

Even though previous COF studies have demonstrated their great potential for a broad range of thermal applications, only a few COF structures have been investigated so far. Moreover, most of the results are based on MD simulations, and there is still a lack of experimental verifications. For the MD simulations, it is still challenging to describe all of the atomic interactions in the COFs, and describing interactions between guests and the COFs is even harder. The experimental efforts to study the thermal transport processes in COFs are limited by the difficulty in synthesizing high-quality crystalline COFs with large sizes. In addition, no experimental data on in-plane thermal conductivity have been reported so far, because of the technical challenges. These challenges in MD simulations, COF synthesis, and thermal property measurements are mutually complementary, as illustrated in Figure 4, and should be addressed in the future for a better understanding of the thermal transport mechanisms in COFs.

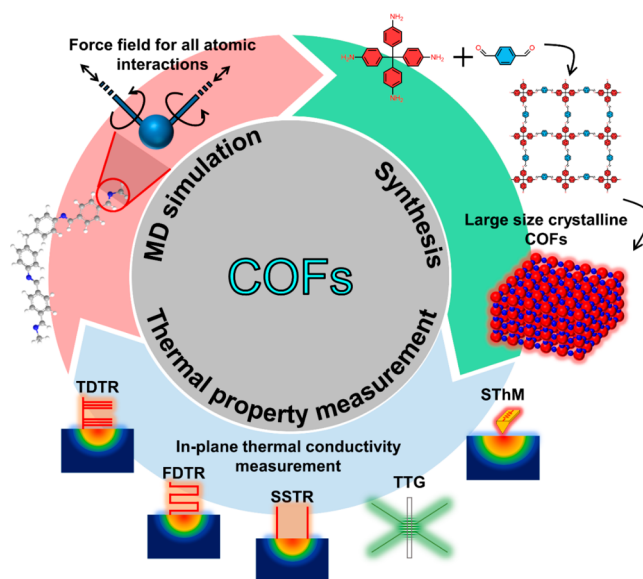


Figure 4. Schematic of current challenges of investigating the thermal transport mechanism in COFs.

MD Simulations. As discussed above, MD simulations have already provided crucial insights into the heat transfer mechanisms in various 2D and 3D COFs. There are ample opportunities in which MD simulations can help guide the design of COFs from a thermal perspective. One of the advantages of MD over methods such as density functional theory (DFT) calculations is the ability of MD simulations to intrinsically account for full-order anharmonicity. For polymeric materials such as COFs that have large unit cells, DFT-based methods involving calculations of higher-order anharmonic interatomic force constants become computationally infeasible. As such, MD simulations, where one can efficiently study large supercells (required to accurately model the vibrational physics), become the practical choice to gain atomistic- and spectral-level insights into the thermal transport properties of COFs. However, one critical limitation of MD simulations is the lack of interatomic potentials for COFs that can accurately describe all of the atomic interactions and replicate their correct vibrational physics.

In general, classical interatomic potentials such as the universal force field (UFF) and polymer consistent force field (PCFF) have had considerable success in correctly describing a range of physical phenomena for several polymeric materials.^{36,37} In fact, PCFF has already been employed to understand the role of pore size on the thermal transport properties of COF-300 and its derivatives.¹⁴ However, these force fields still lack some appropriate parameters to fully describe both the long- and short-range interactions for various COFs. For example, although some classical all-atom force fields, such as the widely used UFF, are able to describe a monolayer sheet of a 2D COF, they are not able to fully replicate the 2D stacked structure with columnar pore geometries in various 2D COFs. This is mainly because the force fields lack key parameters (such as the π - π interactions) that are necessary to keep the columnar pores and the stacked layers intact. In addition, although PCFF can handle nonbonded interactions such as π - π interactions and hydrogen bonds,³⁸ it cannot describe some complicated covalent bonds or interactions between multiple atoms. Therefore, lacking some key parameters required to correctly model all interactions in COFs, these potentials are not fully equipped to study the fundamental thermal transport processes for a wide array of COF structures.

Recent MD simulations utilizing reactive bond order potentials, such as the adaptive intermolecular reactive empirical bond order (AIREBO) potential, have had some success in correctly describing the layered 2D structures for some idealistic COFs.^{12,17,39} These studies have shed light on some crucial heat transfer mechanisms in idealized 2D COFs. However, insights gained from these toy models are still limited, and there is plenty of room for advancements in modeling the correct chemistries and architectures for a range of 2D and 3D COFs. For accurate thermal conductivity predictions and to gain atomistic insights into the thermal transport characteristics of COFs, machine-learning-based interatomic potentials could be pivotal in accounting for all the diverse interatomic interactions necessary to correctly replicate the intricate chemistries and geometries of COFs. These machine learning potentials also provide the prospect of acquiring DFT-level accuracies in MD simulations that are critically important for replicating the correct vibrational physics in COFs.

COF Synthesis. There are still many obstacles in synthesizing high-quality COFs, preparing uniform thin films, and growing crystals suitable for single-crystal X-ray analysis and thermal conductivity measurements. As mentioned in the [Introduction](#), the COF preparation is a compromise between the formation of highly robust chemical bonds (ensuring chemical and thermal material stability) and maintenance of high COF crystallinity (relying on formation of dynamic bonds and self-correction mechanisms).^{25,26} The solvothermal method is a classical approach commonly used to synthesize COFs, but it has various shortcomings, including strict temperature and pressure controls, a longer reaction time, harmful organic solvents, and a complex operating procedure. Alternative growth mechanisms based on nontraditional heating methods and reaction media have been developed. For example, microwave synthesis methods and ionic-liquid-mediated synthesis offer faster, simpler, and more environmentally friendly routes to COF synthesis.⁴⁰⁻⁴² An attractive alternative to existing direct synthetic routes of COF preparation is their postsynthetic modification, i.e. a reliable

method allowing for tailoring material properties after material synthesis. Currently, reconstruction routes for enhancement of framework crystallinity and porosity and on-surface COF synthesis have attracted significant attention of the broader scientific community.^{6,7} Despite significant progress in understanding COF formation mechanisms, current studies are largely limited to COFs linked by borate and imine.⁴² A clear elucidation of the process of COF growth and nucleation is needed to synthesize other types of COFs. Furthermore, current synthesis strategies are primarily applied to 2D COFs, while the field of 3D COFs has shown a slower growth trajectory for two main reasons. First, organic building blocks with multiple reactive groups possessing suitable geometry are less accessible for 3D COFs.⁴³ Second, the orientation of organic building blocks in 3D frameworks is more flexible due to the absence of layered structures and strong π - π interlayer interactions observed in 2D COFs. As a result, the synthesis of 3D COFs is more challenging and can lead to multiple crystalline structures or even amorphous phases, which are typically less stable than 2D COFs. The combination of these factors exhibits a profound influence on the process of crystallization of 3D scaffolds, thereby contributing to the scarcity of 3D COF single-crystal structures reported in the literature to date. To overcome these challenges, further thermodynamic and kinetic studies on COF growth under various reaction conditions are essential, given that the development of 3D COFs is still in its early stages.

Larger than micrometer-sized single crystals of COF are desired for thermal characterization. Fortunately, there have been synthesis efforts to pursue larger COF crystals and they have shown promising results. For example, a large single crystal of 3D imine COF with a size of tens of micrometers was obtained by dynamic control during crystal growth.⁴⁴ 2D COF single crystals with sizes up to 0.2 mm were produced within 2–5 min via the growth in supercritical CO₂.⁴⁵ Nevertheless, the synthesis of large-scale COF single crystals and the formation of highly uniform thin films are still in their early stages. Also, it requires further development to fulfill the requirements of large-scale production that are necessary for thermal measurements and eventually practical applications in industry.

Thermal Conductivity Measurement of COFs. The anisotropic thermal conductivity of 2D COFs gives potential for exceptional heat-spreading solutions on the nanoscale. However, the computationally predicted high in-plane thermal conductivity has never been experimentally validated. This, in part, is due to limitations in the current thin film thermal conductivity metrologies coupled with growth considerations for highly ordered COFs.

Pump-Probe Thermoreflectance Techniques (TDTR, FDTR, and SSSTR). Standard implementations of pump-probe thermoreflectance techniques, such as time-domain thermoreflectance (TDTR), frequency-domain thermoreflectance (FDTR), and steady-state thermoreflectance (SSSTR), are ideal for measurements of cross-plane thermal conductivity. However, their standard implementations make them relatively insensitive to in-plane thermal conductivity for COF thin films because while COFs are strongly anisotropic, the magnitude of their in-plane thermal conductivity is still relatively low and thus will not influence the in-plane heat spreading of the deposited heat from the focused laser spot. Further, the high-quality COF thin films synthesized to date are typically on graphene-templated thin thermal oxides (~100s of nanometers

of SiO₂ on Si wafer) or metals; these substrates dominate the in-plane heat spreading relative to the thin COFs, thus preventing any sensitivity to the in-plane thermal conductivity of the COFs. One possibility to accurately measure the in-plane thermal conductivity of thin COF films would be to use much thicker thermally insulating layers as substrates so that the majority of heat spreading in the measurement volume of a thermoreflectance experiment would be in the COF. This sample configuration would be ideal for a standard SSTR measurement,⁴⁶ which operates in the low-frequency, steady-state regime and thus is inherently more sensitive to in-plane heat transfer or a beam-offset thermoreflectance measurement.⁴⁷ In principle, however, even with current COF sample geometries that are fabricated on thermally conductive substrates or very thin insulating layers, implementing pump–probe thermoreflectance-based measurements with diffraction- or subdiffraction-limited spot size and/or beam offset approaches could enhance the measurement sensitivity to in-plane transport.⁴⁸ In addition, using oblong beam or patterned transducers, such as a 1D metallic grating on a sample surface, may offer a possibility to directly control the directional sensitivity of pump–probe thermoreflectance-based measurements.^{49,50}

Another possibility would be to create suspended COF films for electrothermal-based measurement methods, allowing a more direct assessment of in-plane thermal conductivity without obfuscation from cross-plane diffusion.

Transient Thermal Grating (TTG) Techniques. The laser-based transient thermal grating (TTG) technique is a pump–probe method for measuring the thermal diffusivity of various types of materials, such as bulk crystals, thin films, liquid samples, etc.^{51–53} It is sensitive to in-plane thermal diffusivity, as demonstrated in a 2D hybrid perovskite.⁵³ In the TTG system, the two pulsed pump laser beams overlap and create thermal gratings on the sample surface by interference. The gratings are transient, as they disappear quickly due to the short pulse of the pump laser, and their decay rate can be detected by the diffracted probe laser. This nondestructive, noncontact approach provides an accurate measurement of the in-plane thermal diffusivity, which when multiplied by density and specific heat capacity results in the in-plane thermal conductivity. We have performed preliminary TTG studies on COF thin films and it is feasible. Previous works that applied TTG to other types of porous materials, such as nanoporous silicon membranes and disordered porous silicon, also demonstrate the potential of TTG.^{54,55}

Scanning Thermal Microscopy (SThM). SThM is a scanning probe-based technique that enables measurements of the thermal properties of materials at the nanoscale.⁵⁶ The technique utilizes a specialized probe that is equipped with a resistance temperature detector (RTD). The probe is sensitive to the heat flow between the probe and the sample, which can be monitored by measuring the change in the resistance of the probe. SThM offers several advantages, one of which is its exceptional spatial resolution that goes beyond the diffraction limit. Because the SThM probe can be highly localized, it allows for establishing precise structure–property relationships experimentally and a more direct comparison with MD simulations. AFM has been applied to characterize the structures and orientation of COFs,^{57–59} highlighting the potential to investigate heat transfer at the nanometer scale that other thermal reflectance methods cannot achieve. Another advantage of SThM is its versatility.⁶⁰ It can be

combined with various scanning probe microscopy (SPM) modes, such as electrical or mechanical measurements, as well as topography. This enables a comprehensive characterization by integrating multiple types of data simultaneously. Considering these advantages, SThM holds promise for observing local thermal phenomena with spatial resolution significantly higher than that of other techniques, unraveling the intricate structure–property relationships of COFs.

CONCLUSION

In summary, COFs offer a great platform for a broad range of thermal applications. Thermal conductivities of 2D and 3D COFs are related to density, pore size, and crystallinity as well as crystal network topologies, robust bonds, and degree of conjugation in COFs. The effect of guest–host interactions on the thermal conductivity of COFs depends on their pore size and the type of guest molecules. Incorporating stimuli-responsive moieties as either guests or building units could also be explored to tune the thermal conductivities of COFs. Despite previous efforts to study the thermal behavior of COFs, obtaining a comprehensive understanding of COFs remains challenging due to limitations in atomistic simulations, COF synthesis, and thermal conductivity measurement techniques. We expect that the development of MD simulations incorporating machine learning interatomic potentials, advancements in large-scale crystalline COF synthesis, and in-plane measurement techniques will provide greater insight into the underlying thermal transport mechanisms in COFs. A comprehensive understanding of the thermal transport mechanisms of COFs will contribute to the fundamental understanding of COFs for their thermal applications.

AUTHOR INFORMATION

Corresponding Author

Zhiting Tian – Sibley School of Mechanical and Aerospace Engineering, Cornell University, Ithaca, New York 14853, United States; orcid.org/0000-0002-5098-7507; Email: zt223@cornell.edu

Authors

Jinha Kwon – Sibley School of Mechanical and Aerospace Engineering, Cornell University, Ithaca, New York 14853, United States; orcid.org/0000-0002-5251-7410

Hao Ma – Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, United States; Department of Thermal Science and Energy Engineering, University of Science and Technology of China, Hefei 230026 Anhui, People's Republic of China; orcid.org/0000-0002-6140-0089

Ashutosh Giri – Mechanical, Industrial and Systems Engineering, University of Rhode Island, Kingston, Rhode Island 02881, United States; orcid.org/0000-0002-8899-4964

Patrick E. Hopkins – Department of Mechanical and Aerospace Engineering, University of Virginia, Charlottesville, Virginia 22904, United States; Department of Materials Science and Engineering and Department of Physics, University of Virginia, Charlottesville, Virginia 22904, United States

Natalia B. Shustova – Department of Chemistry and Biochemistry, University of South Carolina, Columbia, South

Carolina 29208, United States; orcid.org/0000-0003-3952-1949

Complete contact information is available at:
<https://pubs.acs.org/10.1021/acsnano.3c03518>

Author Contributions

The final version of the manuscript has received approval from all authors. All authors have participated in the discussions and agreed on the content. J.K. was responsible for writing the draft, while H.M. and N.B.S. contributed information on COF synthesis and reviewed the draft. A.G. provided insights on guest–host interactions and MD simulation in the challenges section and reviewed the manuscript. P.E.H. contributed information on measurement in the challenges section and reviewed the draft. Z.T. conceived the idea of this perspective, led the discussion, and reviewed and revised the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This work was partially funded by Z.T.'s NSF CAREER Award (CBET1839384). This work was partly supported by CHIMES, one of the seven centers in JUMP 2.0, a Semiconductor Research Corporation (SRC) program sponsored by DARPA.

REFERENCES

- (1) Geng, K.; He, T.; Liu, R.; Dalapati, S.; Tan, K. T.; Li, Z.; Tao, S.; Gong, Y.; Jiang, Q.; Jiang, D. Covalent Organic Frameworks: Design, Synthesis, and Functions. *Chem. Rev.* **2020**, *120* (16), 8814–8933.
- (2) Wu, M.-X.; Yang, Y.-W. Applications of Covalent Organic Frameworks (COFs): From Gas Storage and Separation to Drug Delivery. *Chin. Chem. Lett.* **2017**, *28* (6), 1135–1143.
- (3) Kandambeth, S.; Dey, K.; Banerjee, R. Covalent Organic Frameworks: Chemistry beyond the Structure. *J. Am. Chem. Soc.* **2019**, *141* (5), 1807–1822.
- (4) Leith, G. A.; Rice, A. M.; Yarbrough, B. J.; Berseneva, A. A.; Ly, R. T.; Buck III, C. N.; Chusov, D.; Brandt, A. J.; Chen, D. A.; Lamm, B. W.; Stefik, M.; Stephenson, K. S.; Smith, M. D.; Vannucci, A. K.; Pellechia, P. J.; Garashchuk, S.; Shustova, N. B. A Dual Threat: Redox-Activity and Electronic Structures of Well-Defined Donor-Acceptor Fullerene-Covalent-Organic Materials. *Angew. Chem.* **2020**, *132* (15), 6056–6062.
- (5) Sasmal, H. S.; Kumar Mahato, A.; Majumder, P.; Banerjee, R. Landscaping Covalent Organic Framework Nanomorphologies. *J. Am. Chem. Soc.* **2022**, *144* (26), 11482–11498.
- (6) Zhang, W.; Chen, L.; Dai, S.; Zhao, C.; Ma, C.; Wei, L.; Zhu, M.; Chong, S. Y.; Yang, H.; Liu, L.; Bai, Y.; Yu, M.; Xu, Y.; Zhu, X.-W.; Zhu, Q.; An, S.; Sprick, R. S.; Little, M. A.; Wu, X.; Jiang, S.; Wu, Y.; Zhang, Y.-B.; Tian, H.; Zhu, W.-H.; Cooper, A. I. Reconstructed Covalent Organic Frameworks. *Nature* **2022**, *604* (7904), 72–79.
- (7) Sun, K.; Silveira, O. J.; Ma, Y.; Hasegawa, Y.; Matsumoto, M.; Kera, S.; Krejčí, O.; Foster, A. S.; Kawai, S. On-Surface Synthesis of Disilabenzene-Bridged Covalent Organic Frameworks. *Nat. Chem.* **2023**, *15* (1), 136–142.
- (8) Wu, M.-X.; Wang, Y.; Zhou, G.; Liu, X. Sparks from Different Worlds: Collaboration of MOFs and COFs. *Coord. Chem. Rev.* **2021**, *430*, 213735.
- (9) Evans, A. M.; Giri, A.; Sangwan, V. K.; Xun, S.; Bartnof, M.; Torres-Castanedo, C. G.; Balch, H. B.; Rahn, M. S.; Bradshaw, N. P.; Vitaku, E.; Burke, D. W.; Li, H.; Bedzyk, M. J.; Wang, F.; Brédas, J.-L.; Malen, J. A.; McGaughey, A. J. H.; Hersam, M. C.; Dichtel, W. R.; Hopkins, P. E. Thermally Conductive Ultra-Low-k Dielectric Layers Based on Two-Dimensional Covalent Organic Frameworks. *Nat. Mater.* **2021**, *20* (8), 1142–1148.
- (10) Yi, G.; Fu, A.; Li, Y. Computational Design of Flexible Organic Porous Nanotubes. In *2022 IEEE International Flexible Electronics Technology Conference (IFETC)*; 2022; pp 1–2. DOI: 10.1109/IFETC53656.2022.9948483.
- (11) Feng, D.; Feng, Y.; Liu, Y.; Zhang, W.; Yan, Y.; Zhang, X. Thermal Conductivity of a 2D Covalent Organic Framework and Its Enhancement Using Fullerene 3D Self-Assembly: A Molecular Dynamics Simulation. *J. Phys. Chem. C* **2020**, *124* (15), 8386–8393.
- (12) Giri, A.; Hopkins, P. E. Heat Transfer Mechanisms and Tunable Thermal Conductivity Anisotropy in Two-Dimensional Covalent Organic Frameworks with Adsorbed Gases. *Nano Lett.* **2021**, *21* (14), 6188–6193.
- (13) Freitas, S. K. S.; Borges, R. S.; Merlini, C.; Barra, G. M. O.; Esteves, P. M. Thermal Conductivity of Covalent Organic Frameworks as a Function of Their Pore Size. *J. Phys. Chem. C* **2017**, *121* (48), 27247–27252.
- (14) Ma, H.; Aamer, Z.; Tian, Z. Ultrahigh Thermal Conductivity in Three-Dimensional Covalent Organic Frameworks. *Mater. Today Phys.* **2021**, *21*, 100536.
- (15) Liu, Y.; Feng, Y.; Huang, Z.; Zhang, X. Thermal Conductivity of 3D Boron-Based Covalent Organic Frameworks from Molecular Dynamics Simulations. *J. Phys. Chem. C* **2016**, *120* (30), 17060–17068.
- (16) Moscarello, E. M.; Wooten, B. L.; Sajid, H.; Tichenor, L. D.; Heremans, J. P.; Addicoat, M. A.; McGrier, P. L. Thermal Conductivity of Two-Dimensional Benzobisoxazole-Linked Covalent Organic Frameworks with Nanopores: Implications for Thermal Management Applications. *ACS Appl. Nano Mater.* **2022**, *5*, 13787.
- (17) Rahman, M. A.; Dionne, C. J.; Giri, A. Pore Size Dictates Anisotropic Thermal Conductivity of Two-Dimensional Covalent Organic Frameworks with Adsorbed Gases. *ACS Appl. Mater. Interfaces* **2022**, *14* (18), 21687–21695.
- (18) Ma, T.; Li, J.; Niu, J.; Zhang, L.; Etman, A. S.; Lin, C.; Shi, D.; Chen, P.; Li, L.-H.; Du, X.; Sun, J.; Wang, W. Observation of Interpenetration Isomerism in Covalent Organic Frameworks. *J. Am. Chem. Soc.* **2018**, *140* (22), 6763–6766.
- (19) Islamov, M.; Babaei, H.; Anderson, R.; Sezginel, K. B.; Long, J. R.; McGaughey, A. J. H.; Gomez-Gualdrón, D. A.; Wilmer, C. E. High-Throughput Screening of Hypothetical Metal-Organic Frameworks for Thermal Conductivity. *Npj Comput. Mater.* **2023**, *9* (1), 1–12.
- (20) Ma, H.; Ma, Y.; Tian, Z. Simple Theoretical Model for Thermal Conductivity of Crystalline Polymers. *ACS Appl. Polym. Mater.* **2019**, *1* (10), 2566–2570.
- (21) Xu, Y.; Wang, X.; Zhou, J.; Song, B.; Jiang, Z.; Lee, E. M. Y.; Huberman, S.; Gleason, K. K.; Chen, G. Molecular Engineered Conjugated Polymer with High Thermal Conductivity. *Sci. Adv.* **2018**, *4* (3), No. eaar3031.
- (22) Kim, T. W.; Jun, S.; Ha, Y.; Yadav, R. K.; Kumar, A.; Yoo, C.-Y.; Oh, I.; Lim, H.-K.; Shin, J. W.; Ryoo, R.; Kim, H.; Kim, J.; Baeg, J.-O.; Ihee, H. Ultrafast Charge Transfer Coupled with Lattice Phonons in Two-Dimensional Covalent Organic Frameworks. *Nat. Commun.* **2019**, *10* (1), 1873.
- (23) Chen, X.; Wang, Y.; Wang, J.; Liu, J.; Sun, S.; Zhu, L.; Ma, Q.; Zhu, N.; Wang, X.; Chen, J.; Yan, W. A COF-like Conductive Conjugated Microporous Poly(Aniline) Serving as a Current Collector Modifier for High-Performance Li-S Batteries. *J. Mater. Chem. A* **2022**, *10* (3), 1359–1368.
- (24) Ma, H.; O'Donnell, E.; Tian, Z. Tunable Thermal Conductivity of π -Conjugated Two-Dimensional Polymers. *Nanoscale* **2018**, *10* (29), 13924–13929.
- (25) Wang, P.-L.; Ding, S.-Y.; Zhang, Z.-C.; Wang, Z.-P.; Wang, W. Constructing Robust Covalent Organic Frameworks via Multi-component Reactions. *J. Am. Chem. Soc.* **2019**, *141* (45), 18004–18008.
- (26) Li, X.; Cai, S.; Sun, B.; Yang, C.; Zhang, J.; Liu, Y. Chemically Robust Covalent Organic Frameworks: Progress and Perspective. *Matter* **2020**, *3* (5), 1507–1540.

- (27) Leith, G. A.; Martin, C. R.; Mayers, J. M.; Kittikhunnatham, P.; Larsen, R. W.; Shustova, N. B. Confinement-Guided Photophysics in MOFs, COFs, and Cages. *Chem. Soc. Rev.* **2021**, *50* (7), 4382–4410.
- (28) Liu, K.; Qi, H.; Dong, R.; Shivhare, R.; Addicoat, M.; Zhang, T.; Sahabudeen, H.; Heine, T.; Mannsfeld, S.; Kaiser, U.; Zheng, Z.; Feng, X. On-Water Surface Synthesis of Crystalline, Few-Layer Two-Dimensional Polymers Assisted by Surfactant Monolayers. *Nat. Chem.* **2019**, *11* (11), 994–1000.
- (29) Dionne, C. J.; Rahman, M. A.; Hopkins, P. E.; Giri, A. Supramolecular Interactions Lead to Remarkably High Thermal Conductivities in Interpenetrated Two-Dimensional Porous Crystals. *Nano Lett.* **2022**, *22* (7), 3071–3076.
- (30) Brozek, C. K.; Michaelis, V. K.; Ong, T.-C.; Bellarosa, L.; López, N.; Griffin, R. G.; Dinca, M. Dynamic DMF Binding in MOF-5 Enables the Formation of Metastable Cobalt-Substituted MOF-5 Analogues. *ACS Cent. Sci.* **2015**, *1* (5), 252–260.
- (31) Akimbekov, Z.; Wu, D.; Brozek, C. K.; Dinca, M.; Navrotsky, A. Thermodynamics of Solvent Interaction with the Metal-Organic Framework MOF-5. *Phys. Chem. Chem. Phys.* **2016**, *18* (2), 1158–1162.
- (32) DeCoster, M. E.; Babaei, H.; Jung, S. S.; Hassan, Z. M.; Gaskins, J. T.; Giri, A.; Tiernan, E. M.; Tomko, J. A.; Baumgart, H.; Norris, P. M.; McGaughey, A. J. H.; Wilmer, C. E.; Redel, E.; Giri, G.; Hopkins, P. E. Hybridization from Guest-Host Interactions Reduces the Thermal Conductivity of Metal-Organic Frameworks. *J. Am. Chem. Soc.* **2022**, *144* (8), 3603–3613.
- (33) Williams, D. E.; Rietman, J. A.; Maier, J. M.; Tan, R.; Greytak, A. B.; Smith, M. D.; Krause, J. A.; Shustova, N. B. Energy Transfer on Demand: Photoswitch-Directed Behavior of Metal-Porphyrin Frameworks. *J. Am. Chem. Soc.* **2014**, *136* (34), 11886–11889.
- (34) Shin, J.; Sung, J.; Kang, M.; Xie, X.; Lee, B.; Lee, K. M.; White, T. J.; Leal, C.; Sottos, N. R.; Braun, P. V.; Cahill, D. G. Light-Triggered Thermal Conductivity Switching in Azobenzene Polymers. *Proc. Natl. Acad. Sci. U. S. A.* **2019**, *116* (13), 5973–5978.
- (35) Shin, J.; Kang, M.; Tsai, T.; Leal, C.; Braun, P. V.; Cahill, D. G. Thermally Functional Liquid Crystal Networks by Magnetic Field Driven Molecular Orientation. *ACS Macro Lett.* **2016**, *5* (8), 955–960.
- (36) Ma, H.; Tian, Z. Chain Rotation Significantly Reduces Thermal Conductivity of Single-Chain Polymers. *J. Mater. Res.* **2019**, *34* (1), 126–133.
- (37) Wei, X.; Wang, Z.; Tian, Z.; Luo, T. Thermal Transport in Polymers: A Review. *J. Heat Transfer* **2021**, *143*, 072101.
- (38) Ma, H.; Li, C.; Tian, Z. Hydrogen Bonds Significantly Enhance Out-of-Plane Thermal and Electrical Transport in 2D Graphamid: Implications for Energy Conversion and Storage. *ACS Appl. Nano Mater.* **2020**, *3* (11), 11090–11097.
- (39) Giri, A.; Evans, A. M.; Rahman, M. A.; McGaughey, A. J. H.; Hopkins, P. E. Highly Negative Poisson's Ratio in Thermally Conductive Covalent Organic Frameworks. *ACS Nano* **2022**, *16* (2), 2843–2851.
- (40) Campbell, N. L.; Clowes, R.; Ritchie, L. K.; Cooper, A. I. Rapid Microwave Synthesis and Purification of Porous Covalent Organic Frameworks. *Chem. Mater.* **2009**, *21* (2), 204–206.
- (41) Stewart, D.; Antypov, D.; Dyer, M. S.; Pitcher, M. J.; Katsoulidis, A. P.; Chater, P. A.; Blanc, F.; Rosseinsky, M. J. Stable and Ordered Amide Frameworks Synthesised under Reversible Conditions Which Facilitate Error Checking. *Nat. Commun.* **2017**, *8* (1), 1102.
- (42) Xiao, J.; Chen, J.; Liu, J.; Ihara, H.; Qiu, H. Synthesis Strategies of Covalent Organic Frameworks: An Overview from Nonconventional Heating Methods and Reaction Media. *Green Energy Environ.* **2022**, DOI: 10.1016/j.gee.2022.05.003.
- (43) Zhu, Q.; Wang, X.; Clowes, R.; Cui, P.; Chen, L.; Little, M. A.; Cooper, A. I. 3D Cage COFs: A Dynamic Three-Dimensional Covalent Organic Framework with High-Connectivity Organic Cage Nodes. *J. Am. Chem. Soc.* **2020**, *142* (39), 16842–16848.
- (44) Ma, T.; Kapustin, E. A.; Yin, S. X.; Liang, L.; Zhou, Z.; Niu, J.; Li, L.-H.; Wang, Y.; Su, J.; Li, J.; Wang, X.; Wang, W. D.; Wang, W.; Sun, J.; Yaghi, O. M. Single-Crystal x-Ray Diffraction Structures of Covalent Organic Frameworks. *Science* **2018**, *361* (6397), 48–52.
- (45) Peng, L.; Guo, Q.; Song, C.; Ghosh, S.; Xu, H.; Wang, L.; Hu, D.; Shi, L.; Zhao, L.; Li, Q.; Sakurai, T.; Yan, H.; Seki, S.; Liu, Y.; Wei, D. Ultra-Fast Single-Crystal Polymerization of Large-Sized Covalent Organic Frameworks. *Nat. Commun.* **2021**, *12* (1), 5077.
- (46) Braun, J. L.; Olson, D. H.; Gaskins, J. T.; Hopkins, P. E. A Steady-State Thermoreflectance Method to Measure Thermal Conductivity. *Rev. Sci. Instrum.* **2019**, *90* (2), 024905.
- (47) Feser, J. P.; Cahill, D. G. Probing Anisotropic Heat Transport Using Time-Domain Thermoreflectance with Offset Laser Spots. *Rev. Sci. Instrum.* **2012**, *83* (10), 104901.
- (48) Karna, P.; Hoque, M. S. B.; Thakur, S.; Hopkins, P. E.; Giri, A. Direct Measurement of Ballistic and Diffusive Electron Transport in Gold. *Nano Lett.* **2023**, *23* (2), 491–496.
- (49) Zeng, L.; Collins, K. C.; Hu, Y.; Luckyanova, M. N.; Maznev, A. A.; Huberman, S.; Chiloyan, V.; Zhou, J.; Huang, X.; Nelson, K. A.; Chen, G. Measuring Phonon Mean Free Path Distributions by Probing Quasiballistic Phonon Transport in Grating Nanostructures. *Sci. Rep.* **2015**, *5* (1), 17131.
- (50) Li, M.; Kang, J. S.; Hu, Y. Anisotropic Thermal Conductivity Measurement Using a New Asymmetric-Beam Time-Domain Thermoreflectance (AB-TDTR) Method. *Rev. Sci. Instrum.* **2018**, *89* (8), 084901.
- (51) Käding, O. W.; Skurk, H.; Maznev, A. A.; Matthias, E. Transient Thermal Gratings at Surfaces for Thermal Characterization of Bulk Materials and Thin Films. *Appl. Phys. A: Mater. Sci. Process.* **1995**, *61* (3), 253–261.
- (52) Li, C.; Ma, Y.; Tian, Z. Thermal Switching of Thermoresponsive Polymer Aqueous Solutions. *ACS Macro Lett.* **2018**, *7* (1), 53–58.
- (53) Li, C.; Ma, H.; Li, T.; Dai, J.; Rasel, Md. A. J.; Mattoni, A.; Alatas, A.; Thomas, M. G.; Rouse, Z. W.; Shragai, A.; Baker, S. P.; Ramshaw, B. J.; Feser, J. P.; Mitzi, D. B.; Tian, Z. Remarkably Weak Anisotropy in Thermal Conductivity of Two-Dimensional Hybrid Perovskite Butylammonium Lead Iodide Crystals. *Nano Lett.* **2021**, *21* (9), 3708–3714.
- (54) Duncan, R. A.; Romano, G.; Sledzinska, M.; Maznev, A. A.; Péraud, J.-P. M.; Hellman, O.; Sotomayor Torres, C. M.; Nelson, K. A. Thermal Transport in Nanoporous Holey Silicon Membranes Investigated with Optically Induced Transient Thermal Gratings. *J. Appl. Phys.* **2020**, *128* (23), 235106.
- (55) Vega-Flick, A.; Pech-May, N. W.; Cervantes-Alvarez, F.; Estevez, J. O.; Alvarado-Gil, J. J. Thermal Conductivity Reduction in Highly Doped Mesoporous Silicon: The Effect of Nano-Crystal Formation. *J. Appl. Phys.* **2018**, *124* (8), 085101.
- (56) Zhang, Y.; Zhu, W.; Hui, F.; Lanza, M.; Borca-Tasciuc, T.; Muñoz Rojo, M. A Review on Principles and Applications of Scanning Thermal Microscopy (SThM). *Adv. Funct. Mater.* **2020**, *30* (18), 1900892.
- (57) Chandra, S.; Kandambeth, S.; Biswal, B. P.; Lukose, B.; Kunjir, S. M.; Chaudhary, M.; Babarao, R.; Heine, T.; Banerjee, R. Chemically Stable Multilayered Covalent Organic Nanosheets from Covalent Organic Frameworks via Mechanical Delamination. *J. Am. Chem. Soc.* **2013**, *135* (47), 17853–17861.
- (58) Kang, Z.; Peng, Y.; Qian, Y.; Yuan, D.; Addicoat, M. A.; Heine, T.; Hu, Z.; Tee, L.; Guo, Z.; Zhao, D. Mixed Matrix Membranes (MMMs) Comprising Exfoliated 2D Covalent Organic Frameworks (COFs) for Efficient CO₂ Separation. *Chem. Mater.* **2016**, *28* (5), 1277–1285.
- (59) Wang, L.; Lu, C.; Yan, H.; Wang, D. Substrate Orientation Effect in Covalent Organic Frameworks/2D Materials Heterostructure by High-Resolution Atomic Force Microscopy. *Nano Res.* **2023**, DOI: 10.1007/s12274-023-5704-0.
- (60) Dietzel, D.; Chotikaprakhan, S.; Bein, B. K.; Pelzl, J. Analysis of Active Semiconductor Structures by Combined SThM and SThEM. *J. Phys. IV Proc.* **2005**, *125*, 87–91.